



RIGA TECHNICAL  
UNIVERSITY

**Juris Treijs**

# **FERROMAGNETIC SORBENTS AND THEIR POTENTIAL FOR COLLECTING POLLUTION WITH SPILLED OIL PRODUCTS**

Summary of the Doctoral Thesis



**RIGA TECHNICAL UNIVERSITY**  
Faculty of Civil Engineering  
Institute of Heat, Gas and Water Technology  
Scientific Laboratory of Powder Materials of the Research Centre of Civil  
Engineering

**Juris Treijs**  
Doctoral Student of the Study Programme  
“Heat, Gas and Water Technology”

**FERROMAGNETIC SORBENTS AND THEIR  
POTENTIAL FOR COLLECTING POLLUTION  
WITH SPILLED OIL PRODUCTS**

**Summary of the Doctoral Thesis**

Scientific supervisors  
Professor Dr. habil. sc. ing.  
**VIKTORS MIRONOVS**  
Professor Dr. sc. ing.  
**EDMUNDS TEIRUMNIEKS**

RTU Press  
Riga 2018

Treijs J. Ferromagnetic Sorbents and their Potential for Collecting Pollution with Spilled Oil Products. Summary of the Doctoral Thesis. – Riga: 2018, 38 p.

Published in accordance with the decision of the Promotion Council 12.03.2018. No. 175.14.



INVESTING IN YOUR FUTURE



EUROPEAN UNION

The presented Thesis has been developed with the support from the European Social Fund within the project “Support for the Implementation of Doctoral Study Programmes in Rezekne Higher Education Institution”

ISBN 978-9934-22-082-1 (print)

ISBN 978-9934-22-083-8 (pdf)

**DOCTORAL THESIS PROPOSED TO RIGA TECHNICAL UNIVERSITY  
FOR THE PROMOTION TO THE SCIENTIFIC DEGREE OF DOCTOR OF  
ENGINEERING SCIENCES**

To be granted the scientific degree of Doctor of Engineering Sciences, the present Doctoral Thesis has been submitted for the defence at the open meeting of RTU Promotion Council on 8.04.2018, 12.00 AM. at the Faculty of Civil Engineering of Riga Technical University, 6B Kipsalas Street, Room 250.

**OFFICIAL REVIEWERS**

Professor Dr. sc. ing. Anatolijs Borodiņecs,  
Riga Tehchnical University

Associate Professor Ing., Ph. D. (doctor) Andrei Kasperovich,  
Belarusian State Technological University, Belarusia

Ph. D. Ina Pundienė  
Vilnius Gediminas Technical University, Lithuania

**DECLARATION OF ACADEMIC INTEGRITY**

I hereby declare that the Doctoral Thesis submitted for the review to Riga Technical University for the promotion to the scientific degree of Doctor of Engineering Sciences is my own. I confirm that this Doctoral Thesis had not been submitted to any other university for the promotion to a scientific degree.

Name Surname ..... (signature)

Date: .....

The Doctoral Thesis has been written in Latvian. It consists of Introduction; 3 chapters; Conclusion; 70 figures, 16 tables, 1 appendices, the total number of pages is 98. The Bibliography contains 166 titles.

## ANNOTATION

Juris Treijs has worked on his Thesis “Ferromagnetic Sorbents and their Potential for Collecting Pollution with Spilled Oil Products” at Riga Technical University and in collaboration with Rezekne Academy of Technologies.

The problem of water decontamination from oil pollution is becoming increasingly topical nowadays because of the growing scale of accidents associated with oil spills from large-tonnage vessels and offshore drilling. Fuel leak from oil depots, petrochemical plants, and fixed tanks of large road transport companies inevitably causes pollution getting into the ground and underground waters, as well as into river basins.

Different types of sorbents are used for elimination of the pollution. Therefore, the issue of development of new sorbents is always topical.

The Thesis is dedicated to the development of new sorbents having ferromagnetic characteristics and to researching what can be used for the collection of spilled oil pollution. Ferromagnetic properties of sorbents allow selective collection of pollution by means of modern technological solutions. The Thesis focuses on the use of recycled resources and of industrial waste, which can be applied for creation of porous, including adsorbent materials. In the course of the study, powdered, floating and ferromagnetic characteristics-bearing sorbents, their extraction at the laboratory level from residues of industrial processes were designed and explored. Positive results have been presented by *Comsor 125* as one of the newly acquired sorbents, being capable to absorb up to 1.5 kg oil pollution per 1 kg sorbent. The sorbent model and methodology for its development was created in the course of the work. It has a floating element in its centre, connected with ferromagnetic particles. Use of ferromagnetic particles represents a prospective direction in the water purification sector from the light types of oil pollution. It will make possible collecting of pollution together with ferromagnetic powder from the water surface by means of mechanical and electromagnetic equipment.

In the course of the work, technologies and appliance were developed for spraying of powdered sorbents above the water surface contaminated with oil products. A stand was created to reduce the human factor during performance of the experiments, which used three permanent voltage magnets and electromagnetic equipment for collection of the oil product contamination from the water surface and below the water level in small depths. The Thesis focuses on recovery and reuse of the sorbents.

New products were developed on the basis of extractable sludge to be used as fuel, fuel elements for thermal cutting of concrete and retrieving metal from solutions that can potentially add to the list of products manufactured in Latvia for internal consumption, as well as for export. The results presented in the Thesis are protected by two LV patents.

The findings presented in the Thesis have been published in 6 scientific articles and 8 scientific reports at international conferences.

## INTRODUCTION

Nowadays increasingly growing problem is represented by water decontamination from pollution with oil and oil products (OPs) due to accidents involving oil spills from large-tonnage tankers and from offshore drilling, which are taking place more often. Spills of fuel and other OPs in oil depots, petrochemical plants, from fixed tanks of large road transport undertakings, passing vessels and ships present at the quayside in navigable river basins and port aquatoria, and oil pipeline accidents inevitably cause pollution getting into the ground, underground waters, as well as river basins. Therefore, problem of elimination of the OP pollution from the water surface is of global nature.

### **Topicality of the theme**

Spills of oil products (OPs) into the water represent a very serious environmental disaster, the consequences of which can be devastating for every living being. Small living organisms, flora, birds, fish and many marine mammals are suffering from spills of OPs [1].

Oil is a product of extended breakdown and, when released, very quickly covers the water surface with a dense oil film layer, which hinders access to air and light. It begrims around bird feathers and results in birds losing their ability to maintain heat, to swim and to fly. In order to avoid the above, OPs spilled in the water have to be removed quickly [2].

There are various methods for water decontamination from pollution with oil products: mechanical, physical-chemical and biochemical methods. Each group has its own advantages and disadvantages, concentration and the total pollution amount areas where those are especially effective. In any particular case, complex and multi-layered decontamination technologies must be used, where any method prevails [3].

**The aim of the Thesis** is to develop a sorbent with ferromagnetic properties, examine its properties and possibilities to use in the collection of pollution with spilled oil products, as well as its further use and utilization options.

### **Tasks of the Thesis**

- Literature analysis regarding the existing sorbents, collection techniques of the oil products, as well as further processing of the collected oil products.
- Development of a sorbent with ferromagnetic properties and examination of its properties.
- Development of a method for water decontamination by means of ferromagnetic sorbent.
- Development of a new sorbent functioning model and performance of its analysis.
- Development of the sorbent recovery and recycling method.
- Development of an experimental pilot equipment, which ensures the collection of oil products through magnetic fields.
- Development of recommendations for recovery and reuse of the sorbent.

### **Theses proposed for defence**

1. New materials (ferromagnetic sorbents).
2. Combined sorbent model with ferromagnetic properties.
3. New technological solutions (equipment and technologies for spraying and collection of the sorbent).
4. New proposals for use of the collected materials (regeneration, fuel, antiseptics).
5. New product development (NPD) – use of the sludge as fuel in thermic concrete cutting, sorbents for copper extraction from solutions).

### **Scientific novelty of the Thesis**

- New methodology developed for creation of new types of sorbents with ferromagnetic properties for sorption of oil products.
- A process model proposed for sorption of oil product films from the water surface by means of ferromagnetic particles.
- Analysis provided regarding the impact of the composition and properties of ferromagnetic sorbents on the sorption process.
- New methods offered for the production of composite sorbents with ferromagnetic properties.
- New methods proposed for sorbent spraying and sludge removal from water by means of magnetic and electromagnetic devices.
- Data obtained for thermogravimetric and differential thermal analysis of iron powder-base sorbent and the collected sludge in the temperature range up to 1000 degrees.
- Proposal for use of the collected OPS (oil product sludge) as high temperature fuel product.

### **Practical novelty of the research**

- Some new composite sorbents (*Comsor 125*, *Comsor M*, etc.) developed with magnetic properties.
- New types of ferromagnetic sorbents developed on the basis of use of technological residues and natural raw materials.
- Stands developed, designed and tested for spraying sorbents on the water surface contaminated with oil products for study of the processes.
- Stands developed, designed and tested for collection of the sludge by means of magnetic and electromagnetic equipment.
- New sorbent recovery and reuse technology proposed.
- New ways for the use of sludge proposed, sorbents obtained with oil products (for concrete cutting with gas flame, production of fuel emulsions and copper extraction from solutions).

**The novelty of research is approved by two Latvian patents (see Annex 1.2).**

### **Approbation of Thesis**

Pursuant to the results of research carried out in the present Thesis, 16 scientific papers have been published in Latvian, Russian and English, including 6 scientific articles and 8 scientific report theses for international conferences, and 2 patents have been obtained. They have examined the oil product sorption processes, creation of powdered ferromagnetic sorbent and characteristics thereof.

### **International publications in reviewed editions**

1. Treijs, J., Teirumnieks, E., Mironovs, V. Environmental pollution with oil products and review of possibilities for collection thereof. Vide. Tehnoloģija. Resursi: VIII starptautiskās zinātniski praktiskās konferences materiāli: Rezekne, Latvia, 2011, 301.–309.
2. Lapkovskis, V., Mironovs, V., Treijs, J., Teirumnieks, E. Collection of spilled oil products by means of ferromagnetic powder materials. Riga Technical University 53<sup>rd</sup> International Scientific Conference: Dedicated to the 150<sup>th</sup> Anniversary of Riga Polytechnical Institute / RTU Alumni: Digest: Riga, Latvia, 2012, 391.
3. Mironov, V., Zemchenkov, V., Lapkovskiy, V., Treis, Y., Savich, V. Investigation of powder ferromagnetic sorbents properties for petroleum collection from water surface

- (Исследования свойств порошковых ферромагнитных сорбентов для сбора нефтепродуктов с водной поверхности) *Ekologicheskiy vestnik*, 2013, 1(23), 32–40.
4. Treijs, J., Teirumnieks, E., Mironovs, V., Lapkovskis, V., Šiškins, A. Investigations of properties of powdered ferromagnetic sorbents. In Proceedings of the 9<sup>th</sup> International Scientific and Practical Conference "Environment. Technology. Resources": Rēzekne, Latvija, 2013, 1, 95–100.
  5. Shishkin, A., Mironovs, V., Lapkovskis, V., Treijs, J., Teirumnieks, E. Ferromagnetic composite for oil spill collection, its properties and morphology. International Conference "Innovative Materials, Structures and Technologies": Riga, Latvia, 2013, 46 p.
  6. Shishkin, A., Mironovs, V., Lapkovskis, V., Treijs, J., Korjakins, A. Ferromagnetic sorbents for collection and utilization of oil products. *Key Eng. Mater.*, 2014, 604, pp.122–125.

#### **Scientific publications (indexed in SCOPUS data base)**

1. Treijs, J., Teirumnieks, E., Mironovs, V., Lapkovskis, V., Shishkin, A., "Investigations of properties of powdered ferromagnetic sorbents," in *Vide. Tehnologija. Resursi - Environment, Technology, Resources*, 2013, Vol. 1, pp. 95–102.
2. Shishkin, A., Mironovs, V., Lapkovskis, V., Treijs, J., Korjakins, A. "Ferromagnetic Sorbents for Collection and Utilization of Oil Products," *Key Eng. Mater.*, Vol. 604, pp. 122–125, 2014. doi:10.4028/www.scientific.net/KEM.604.122).

#### **Journals**

1. Mironov, V., Zemchenkov, V., Lapkovskiy, V., Treis, Y., Savich, V. Investigation of powder ferromagnetic sorbents properties for petroleum collection from water surface (Исследования свойств порошковых ферромагнитных сорбентов для сбора нефтепродуктов с водной поверхности). *Экологический вестник*. Nr. 1 (23). Minsk, Belorussia, 2013, 32–40.

#### **Participation at conferences and congresses**

1. Mironovs, V., Lapkovskis, V., Treijs, J. Ferromagnetic sorbents for collection and utilization of oil products. International Scientific Conference "Materials Engineering", Kaunas, Lithuania, 2011.
2. Šiškins, A., Treijs, J., Mironovs, V., Lapkovskis, V. Investigation of Ferromagnetic Metal – Ceramic Adsorbent Materials. 8<sup>th</sup> International Conference "MET – 2013". Riga, Latvia, 19 June 2013.
3. Lapkovskis, V., Mironovs, V., Treijs, J. Criteria methods in evaluation of peat materials properties. 8<sup>th</sup> International Conference "MET – 2013": Riga, Latvia, 19 June 2013.
4. Treijs, J., Mironovs, V. Investigations of Properties of Powdered Ferromagnetic Sorbents. 9<sup>th</sup> International Scientific and Practical Conference "Environment. Technology. Resources", Rezekne, Latvia, 22 June 2013.
5. Shishkin, A., Mironovs, V., Lapkovskis, V., Treijs, J., Korjakins, A. Ferromagnetic Sorbents for Collection and Utilization of Spilled Oil Products. International Scientific Conference "Baltmattrib 2013". Riga, Latvia, 14 November 2013.
6. Treijs, J., Teirumnieks, E., Lapkovskis, V., Mironovs, V. Sorbents for Collection of Oil Products. 4<sup>th</sup> Symposium "Verbundwerkstoffe und Werkstoffverbunde". Dresden, Germany, 18 November 2013.
7. Shishkin, A., Mironovs, V., Lapkovskis, V., Treijs, J., Teirumnieks, E., "Ferromagnetic composite sorbents for oil spill collection, its properties and morphology. International Conference "Innovative Materials, Structures and Technologies". Riga, Latvia, 2013.



8. Treijs, J., Mironovs, V., Teirumnieks, E. Investigations of properties of powdered ferromagnetic Sorbents. 9<sup>th</sup> International Scientific and Practical Conference "Environment. Technology. Resources", Rezekne, Latvia, 2013.
9. Shishkin, A., Mironovs, V., Lapkovskis, V., Treijs, J., Teirumnieks, E. Ferromagnetic composite sorbents for oil spill collection, its properties and morphology. International Conference "Innovative Materials, Structures and Technologies", Riga, Latvia, 2013.
10. Treijs, J., Mironovs, V. Increase of efficiency of application of ferromagnetic sorbents at collection of oil products spilled in water. 6<sup>th</sup> International Symposium: Porous permeable materials: technologies and products. Minsk, Rakov, Belorussia, 19 October 2017.

**National patents:**

1. Šiškins, A., Mironovs, V., Treijs, J., Baroniņš, J. Sorbents ar feromagnētiskām īpašībām. Pat. LV 14822 B (20.06.2014.).
2. Šiškins, A., Mironovs, V., Treijs, J., Feromagnētiskais sorbents. Pat. LV 14820 B (20. 06. 2014.).

## TABLE OF CONTENTS

<b>1. COLLECTION OF OIL PRODUCTS (ANALYTICAL PART)</b> .....	10
1.1. Oil pollution problems .....	10
1.2. Methods for Collection of the Oil Products .....	11
1.3. Sorbents .....	13
1.4. Overview of ferromagnetic sorbents.....	14
1.5. Potential components for production of composite sorbents from lightweight materials .....	15
<b>2. THEORETICAL PART</b> .....	17
2.1. Combined ferromagnetic sorbent model.....	17
2.2. Impact of the magnetic field on fine-dispersed particles in the water .....	18
<b>3. METHODOLOGICAL PART</b> .....	19
3.1. Experimental research methodology, methods and equipment .....	19
3.2. Materials used for the research .....	22
<b>4. CREATION OF THE COMPOSITE FERROMAGNETIC SORBENT (EXPERIMENTAL PART)</b> .....	23
<b>5. NOVELTY OF THE THESIS</b> .....	26
<b>6. CONCLUSIONS</b> .....	27
<b>ABBREVIATIONS AND SYMBOLS USED IN THE THESIS</b> .....	29
<b>BIBLIOGRAPHY</b> .....	30
<b>APPENDICES</b> .....	38

# 1. COLLECTION OF OIL PRODUCTS (ANALYTICAL PART)

## 1.1. Oil Pollution Problems

Oil is a mixture of hydrocarbons having different molecular weights and diverse boiling temperature and density of 0.82–0.92 g/cm<sup>3</sup> [21]. With distillation method it is divided into separate oil products (OPs): petrol containing some lightest hydrocarbons, naphta containing hydrocarbons with high numbers of carbon atoms, kerosene, and gas oil.

After these products are distilled, a black, viscous liquid – heavy fuel oil – is left over from oil. Lubricant oils are obtained from heavy fuel oil by means of distillation, for lubrication of different mechanisms. Distillation is carried out at a reduced pressure, in order to reduce hydrocarbon boiling temperature and to avoid decomposition when heated. Non-volatile dark mass – goudron to be used for street asphaltting – is left over after the oil distillation. The most important products to be derived from oil are shown in Table 1.1 [22].

Solid hydrocarbons are extracted from certain varieties of oil – so-called paraffin (used, for example, in candle-making) and vaseline, which is a mixture of liquid and solid hydrocarbons [23]. Apart from processing in lubricating oils, the heavy fuel oil is used as fuel in plant boiler spaces, where it is administered with the help of nozzles.

Table 1.1

Main Types of Oil Products

Types of oil products		Boiling temperature, °C	
Petrol		40–200	
Naphta		25–50	
Kerosene		120–240	
Gas oil		150–310	
Heavy fuel oil	Lubricatin g oils	Spindle oil, motor oil, cilinder et al. oils 300–350 350–400	
	Vaseline		230–255
	Paraffin		250–270
	Goudron		380–420

Heavy fuel oil shall mean a mixture of organic compounds containing hydrocarbons (having molecular weight of 400 to 1000), oil resin (having molecular weight of 500 to 3000 and more), asphaltene, karben and metals (V, Ni, Fe, Mg, Na, Ca). Physical and chemical properties of the heavy fuel oil are dependent on the original oil composition and distillation of the distillate fractions and their typical data are as follows: viscosity 8–80 mm<sup>2</sup>/c (at 100 °C), density 0.89–1 g/cm<sup>3</sup> (at 20 °C), solidification point 10–40 °C, sulphur content 0.5–3.5 %, ashes up to 0.3 %, low calorific value 39.4–40.7 MJ/mol.

Operations of industrial companies, oil depots, rail and road transport, as well as maritime and river vessels result in significant quantities of OP waste in the form of fuel waste, bottom sediments, exhaust oils. These products are posing high danger to the environment [25], in particular in the case where these products are present in large amounts.

## 1.2. Methods for Collection of the Oil Products

Decontamination of nature from oil can be divided into three modes [32], [33]:

- 1) water decontamination from OPs;
- 2) decontamination of coastal zone;
- 3) decontamination of polluted soil.

While according to elimination methods of the oil product spills they can be divided according to the collection/liquidation principle:

- 1) mechanical type;
- 2) chemical type.

### Liquidation of the consequences for oil product spills by mechanical means – booms

In liquidation of the consequences of oil spills priority is given to mechanical collection of oil products, first, via their localization. The most common type for localization of spilled oil is enclosing further spread of the pollution with booms and then collection thereof by means of mechanical appliances.

Containment booms (booms) are consisting of floating barriers provided for localization of distribution of OPs discharged in water and transportation thereof at a small distance [34].

General boom structure is shown in Figs. 1.1. and 1.2.

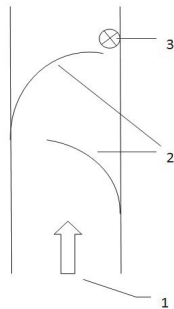


Fig.1.1. Cross-sectional draft of the booms:

- 1 – plastic material, which performs the OP holding function;
- 2 – floating material, which performs retaining on the water surface;
- 3 – sinking material, which performs the plastic material (1) tensioning function by not allowing its spinning. Blue line shows the water level.

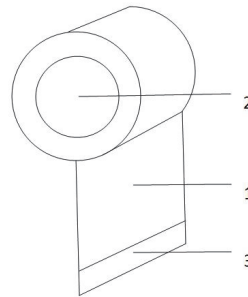


Fig. 1.2. Principal scheme for operation of the containment type booms:

- 1 – river stream direction;
- 2 – adsorbent booms;
- 3 – mechanical oil collection.

### Mechanical OP removal from the water surface

After localization of the oil products their collection may be commenced. Most commonly it is carried out by means of mechanical devices – skimmers. There are several types of receivers: floating, screws, rope, tape, etc. [33], [38].

All the floating receivers are essentially pumps, inlet of which is located under the water level and, when operation starts, they commence drawing in the oil film formed on the water surface.

Screw receivers are operating in the same way as all the receivers described below, they have one peculiarity reflected in their name – the receiver component, which receives the oil product and delivers it to the storage bin.

### OP collection from the water surface by means of chemical substances

In exceptional cases, in order to prevent pollution of particularly sensitive maritime coastal areas with OP, spilled oil can be treated with dispersants, unless authorisation has been issued for use of dispersants and oil spill has not been emulsified yet [39]. Dispersants are represented by various types of chemical detergents, which are sprayed over oil spots from aircrafts or boats. The chemicals are splitting oils in very tiny drops, which are vertically distributed in the water. Use of dispersants speeds up the physical and chemical degradation processes, which would have taken place naturally. Dispersants can be sprayed directly over oil spots by means of special floating stations or aircrafts. Impact of dispersants on the oil products in water and operating principle at the molecular level is generally shown in Fig 1.3 [40].

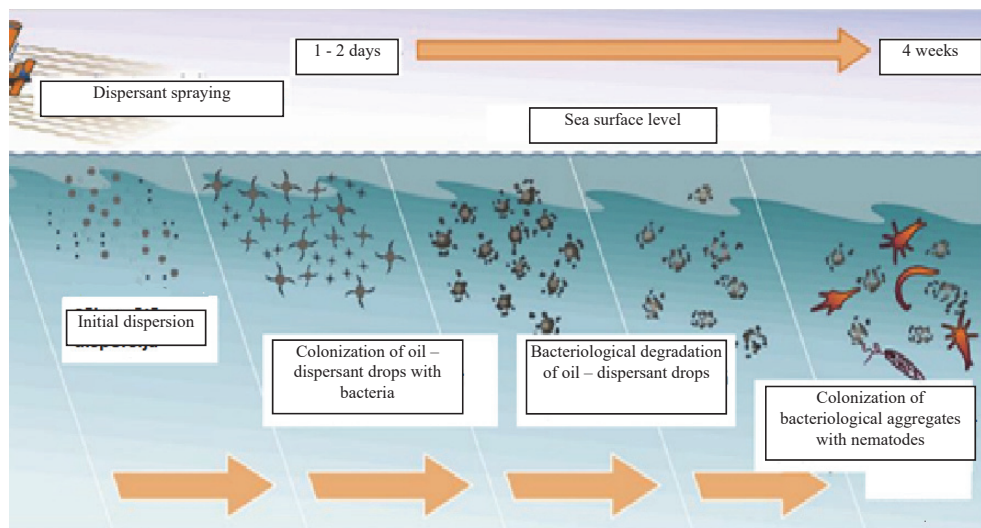


Fig. 1.2. Stages of exposure of spilled oil products to dispersant.

### Decontamination of polluted coastal area

Three basic methods are practically applied for restoration or protection of a polluted coastal area [40].

- 1) If the circumstances warrant it, containment can be installed between the oil slick and the shoreline, thus preventing oil pollution even to reach the shore.
- 2) If it is not possible to set up a containment, then oil slick is sprayed with chemicals in order to avoid splitting of hydrocarbons on the beach. Such treatment prevents the disintegrated oil to adhere to the sand and to the stones situated on the shore, facilitates its collection process, or also promotes natural degradation.
- 3) If the beach is contaminated, there are two options: treatment of the coastline with the already mentioned chemicals or mechanical collection of oil.

One of the collection facilities is of a trailer type, which is dragged by any construction machines, for example, tractor. This appliance decontaminates sand or grass with springs cut across points, penetrating into the sand and bringing oil lumps into the mouldboard further diverted into hydraulic tank on the machine rear.

### **Decontamination of polluted soil**

Removal of pollution from contaminated soil is carried out by physical and chemical means. These processes are trying to separate harmful substances from soil, sand or abrasive material. Separation may be done using different methods [42].

*Separation by means of gravity.* This process may be based on different densities between the solution stages. The size of device and effectiveness of decontamination by means of gravity is dependent on speed adjustment of the spread of oil or its products, size of the substance particles, density difference, viscosity and concentration of the particles. Separation with gravity is applied also in order to dispose of immiscible oil layers and to classify particles with different dimensions. Typically coagulation and flotation is used beforehand in order to increase the size of the particles, which facilitates the separation process.

*Physical separation by means of sieve.* Separation process uses sieves of different sizes and screens in order to effectively concentrate oil and its products in smaller quantities. Physical separation is based on the fact that organic and inorganic substances are mutually connecting both chemically and physically, particularly it is expressed in clay and sludge. Clay and sludge particles are physically attached to coarse sand or soil, which perfectly concentrates OP in a little volume unit, hence it is easier to process. The biggest advantage of physical separation is that a high level of purification can be achieved with a relatively small number of devices. However, there is a range of factors present, which may limit effectiveness and practicality of both these processes. One of these is high clay and moisture content of the soil, which increases the decontamination costs. In separation by means of gravity the processes are based on different specific weights of solids and solution.

*Soil washing.* In the course of soil washing process the water is saturated with the washing agent, surface active substances, pH regulatory substances or colloid agents, which assist in separation of organic substances. During the soil washing process the poisons are separated in two ways – by releasing or by creating other substances, as well as by collecting the same in small quantities in high concentrations [43].

The concept of decontamination of the polluted soil with particulate matter reduction is based on the fact that the OP has a tendency towards physical or chemical binding with clay, sludge or organic soil particles. While the clay and sludge is bound to the sand with natural methods such as compression and adhesion. Washing process separates not only clay and sand from the soil, but also reduces the oil product particles in soil to make it easier to work with the same afterwards. This method also contains a number of factors, which may limit effectiveness and applicability of the process. When washing the soil contaminated with OP, many and different unnecessary solutions (e.g. organic substances + metals) may emerge, which requires additional processing, and therefore the costs are increased and the purification process gets complicated. High humus content of the soil can increase major costs, because it is difficult to separate humic substances in loamy soils. Saturated water also requires additional processing and demobilisation.

### **1.3. Sorbents**

Different sorbents are widely used for collection of OPs spilled in water, hence natural and artificial [51], [52] sorbents are used as materials with a developed surface. They are charged with a number of requirements: maximum available sorption volume, flowability, buoyancy,

small weighing down, safety to the environment, resistance to wear (in the event when used in releasable filters), recovery option, etc. (Table 1.2).

Use of asbestos paper and cardboard for water decontamination from OPs [53] is known. In this case, the sorbent recovery is carried out through heating. Polymer sorbents are widespread, which can be recovered by solvents [54] or by extraction [55].

Table 1.2

### Main Characteristics of Bulk Sorbents

<i>Properties</i>	<i>Units of measurement</i>	<i>Range</i>
Sorbition volume	g/g	1.5–50
Bank density	g/cm <sup>3</sup>	2.00–3.80
Fluidity	s	10–20
Moisture	%	Up to 10
Buyoancy	Twenty-four hours	From 2 to 10

Hydrofobised basalt fibre base sorbents are recovered also by squeezing out or by incinerating OP residues [56]. Shavings and sawdust placed in permeable fabric casing [57], to be used as sorbent, may be disposed of by incineration, at the same time producing energy. Granular activated carbon, one of the most wide-ranging sorbents, is also used in water decontamination from OPs [51], [52], [58], [59]. Whereas activated charcoal is expensive as sorbent, which results in its typical use only for additional processing of drinking water.

All the previously mentioned sorbents have another common disadvantage: difficulty in sludge removal from water surface after implementation of the sorption process. It is mainly carried out mechanically – with scraper blades, and rollers. Sometimes sludge pumps [60] are used, working in the increased area of concentration of OPs confined with the boom containment.

Many existing methods for the collection of spilled OP residues facilitate the use of various emulsifiers, including those on the surfactant basis. These methods are related to environmental chemical pollution, their characteristic trait is difficulties in full utilization of materials and increased expenses.

## 1.4. Overview of Ferromagnetic Sorbents

Allocation of magnetic properties to the sorbents can provide considerable efficiency increase thereof, because it opens up a possibility to introduce sorbents in the environment to be decontaminated in the form of dispersity phase at the controllable surface and to extract from the environment by means of magnets and electromagnets [69]–[70]. Papers [71]–[72] consider a possibility to use disperse ferromagnetic sorbents (FMS) for the collection of oil and other oil products at the bottom of watercourses. Several publications have provided new proposals regarding sorbents having magnetic properties and described possibilities of their use in the collection of light fractions of OP products spilled in water. Such operations are carried out in a number of countries. For example, one of the methods is proposed in Odessa (Ukraine) [73].

The Thesis describes “naftaclean” – a product, which is used for the collection of spilled oil. A variety of organic fibre, for example, lignin, soya hulls, agricultural and timber industry residues serve as raw materials for “naftaclean”. Substrate is crushed, then processed in dispersant, removed from the solution and dried. Then additives are produced for ferromagnetic particles. Finely disperse iron base powder FER-3, having a high level of coercive force (up to 30 kA/m), is spread on the spill film. It does not destroy the spill film of oil product but modifies its properties, which creates an opportunity to collect it by means of magnetic devices. The

effectiveness of the method is sufficiently low because the modification process is slow, but the upward thrust is small.

In Riga Technical University, the work on creation of sorbents having ferromagnetic properties and their use in the development of technologies was started in the late 1990s. Simple sorbents from different types of iron powders, as well as fine-cut rolling mill scale were basically used [74], [75]. These sorbents have inherent range of substantial shortcomings. They have low buoyancy and low sorption capacity. These studies have mainly used iron base powder materials: iron powder ASC 100.29 (dusted one, used for the production of constructive components by means of powder metallurgy method), powder MH 80.23 (recombined porous one, for use in the manufacture of automatically lubricating slip bearings), and powder of M20/80-19 (with decreased carbon content) [79]. Powder coarseness is determined by its objective. Powders 40–100 are primarily used for the purpose of production of powder preparations, while powders in the micron and submicron range are used for the production of ferromagnetic suspensions [80]. Such powders are normally used for non-destructive control of the products of mechanical engineering and other sectors.

Magnetic properties of materials are largely determined by chemical composition and density of the substance. Efficiency of technological processes controlled by magnetic or electromagnetic fields is repeatedly dependent therefrom.

Studies have revealed a principled possibility for application of iron powders for sorption of different substances. In addition, it was established that effective use of the method requires resolving of very many tasks: to assess the sorption efficiency and to reduce the costs of sorbents, to increase their buoyancy by means of high-speed magnetic devices, to develop appliances for sorbent spraying and sludge collection.

### **1.5. Potential Components for Production of Composite Sorbents from Lightweight Materials**

The main disadvantage of the iron containing ferromagnetic sorbent materials is their high specific weight, increased oxidizability, and low buoyancy. In this context, components from lightweight materials should be examined for manufacturing of composite sorbents. Attention should be paid to natural light materials such as fine-cut peat, sapropel, and sawdust. At the same time, during recent years products have appeared in the production, such as cenospheres, from technological residues and other ceramic materials.

#### **Ceramic industry waste**

The ceramic industry creates a lot of light easy dispersable technological waste when producing surfacing tiles, bricks, etc. [91]. Their bulk density ranges between 0.45 and 1.5 g/cm<sup>3</sup>. It consists mainly of silica and aluminium oxides. Residues are used for various purposes. For example, certain batch material is used for the production of glass ceramics. It contains 30–60 % of residues from alunda abrasive circle processing in ceramic link (corundum) and 40–70 % of glass obtained by crushing the glass residues.

However, it should be noted that use of such residues in the status of sorbents and their components may cause certain difficulties in relation to the need to carefully define their chemical composition, sorting and pressing into granules. These materials can additionally contaminate the environment.

#### **Aluminosilicate microspheres**

The lightest component, which is formed at the same time with ash, is represented by aluminosilicate microspheres (MSPs), which tend to have extremely low bulk density (0.3–0.5 g/cm<sup>3</sup>), and which are carried away by flue gases together with very fine light ash [93]. These



MSPs together with ashes are getting into ash sedimentation tanks, where, due to their low density they accumulate mainly on the sediment layer surface, and they can easily be taken away by rain and wind. The most dangerous possibility is spreading in the environment by wind, due to the fact that they can travel long distances and penetrate into human and animal respiratory tracts, promoting cardiovascular and respiratory diseases [94]. At the same time, however, MSPs have several unique characteristics, which prospectively make their efficient use in many modern technologies possible. It contributes to the need for improvement of their collection methods, to explore in depth their properties and creation mechanisms, as well as to develop the optimal methods of use [95]. There are two main categories of MSPs: "empty spheres" where the cavities are filled only by gas; so-called cenospheres (CS); and plerospheres (PS) where the cavities are filled with small mineral particles, foam, spongy or some other kind of porous structure. MSPs are created from amorphous, glass like material, which contains amorphous SiO<sub>2</sub> (50–65 weight%), Al<sub>2</sub>O<sub>3</sub> (20–30 weight%), Fe<sub>2</sub>O<sub>3</sub> (1–8 weight%), as well as Ca, Mg, etc., phosphates, sulphates, chlorides, as well as quartz, mullite, etc.

Appropriate assessments are usually obtained from studies regarding a partly broken MSP. CSP has a potential for their use in filters, various types of insulation, anti-corrosion coating, protection layers on a liquid surface in order to reduce evaporation, energy absorbing shock absorbers and other vehicle components, pneumatic tyres, et al. Properties of CSs and ashes are mainly determined by their chemical composition and texture (in this case, texture means the structure at supramolecular level). In some literature sources most of the attention is focused on chemical and phase composition.

## Peat

Peat is one of the most important natural resources in Latvia. Total bog area in Latvia reaches 6401 km<sup>2</sup> or 9.9 % of its total territory.

Peat as a natural sorbent is known for quite a long time and is used in various filters for the purpose of decontamination from organic and oil containing products dissolved in water. Peat morphologic and chemical composition allows it to carry out mechanical decontamination on the account of fibrous structure, as well as biological and chemical decontamination. This makes it one of the most optimal and budgetary options for using it as a filter material in sewage treatment systems [98].

## Sapropel

Sapropel is created at the bottom of freshwater reservoirs, mostly lakes, which do not have running water [101]. After acquiring, it is dried and becomes a powder, which later is pressed in granules or left in bulk. It should be noted that humidity of sapropel in original condition is up to 97 %. It quickly dries down to 55 % of humidity, then dries very slowly. Specific weight in the dried form reaches 1.4–1.7 g/cm<sup>3</sup>. Granules are the most preferable to be used as sorbents (Fig. 1.4).



Fig. 1.3. Dried sapropel granules.

## 2. THEORETICAL PART

Previous studies in the field of sorbents with ferromagnetic properties indicate that it is necessary to further develop methodology for creation of effective sorbent with enhanced sorption and buoyancy, as well as to analyse its interaction with electromagnetic and magnetic systems. Furthermore, it is clear that effective sorbent must be a combined product consisting of several components.

### 2.1. Combined Ferromagnetic Sorbent Model

The new combined sorbent (*Comsor*) proposed by authors [102] is based on a hollow thin-walled microsphere 1, made of ceramic material (Fig. 2.1). It has low specific weight and good buoyancy. Its surface in the original form has a small specific surface. In addition, the microsphere itself usually does not possess magnetic properties. Therefore, by means of binder 2, the surface of microsphere 1 is covered by powdered layer 3 of ferromagnetic particles. Overall effectiveness of such sorbent depends on the magnetic properties of these particles and the conglomerate. Flake-based particles of materials 5 can be applied on the microsphere surface, the task of which is to improve the adhesion with OP.

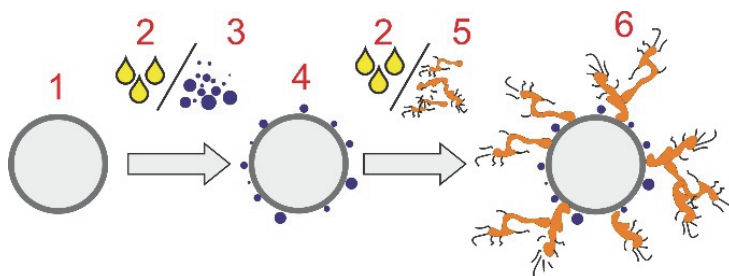


Fig. 2.1. Sorbent building phases:

1 – cenosphere; 2 – binder; 3 – ferruginous powder; 4 – CS *Comsor*;  
5 – peat particles; 6 – CS *Comsor-125*.

OP sorption by means of microspheres is taking place in many processes [103]:

- OP adhesion with ferromagnetic particles by adhesion;
- OP mechanical grip with flake-based elements;
- OP holding between particles with capillary effect (Fig. 2.2).

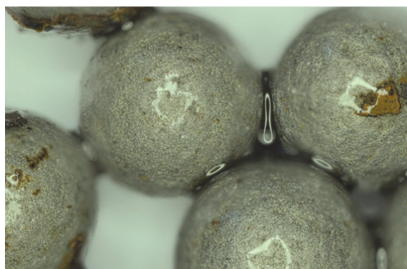


Fig. 2.2. Holding of OP in the cavities formed by the microspheres.

In this case, capillary effects are playing an important role (Fig. 2.3).

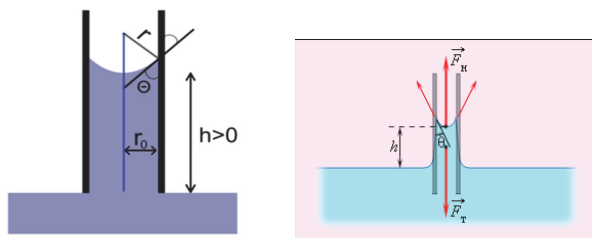


Fig. 2.3. Capillary phenomena scheme (a); and operation of forces in capillary (b).

The formula that determines the height of liquid rise in a capillary (Borelli-Jurin's formula) is described as

$$h = 2\sigma \cos\theta / r_0(p - p_0)g, \quad (2.1)$$

where

- $\sigma$  liquid surface tension coefficient;
- $h$  lifting height of the liquid column;
- $\theta$  angle for moistening of the capillary wall with liquid;
- $g$  free fall acceleration;
- $p$  liquid density;
- $p_0$  gaseous phase density;
- $r_0$  capillary radius.

The smaller the capillary radius  $r_0$ , the higher the liquid rises. The height of a liquid column rise is increasing also with the growth of liquid surface tension coefficient. Liquid rise in the capillary continues until the module of gravity  $F_T$  acting on the liquid column in capillary is equal to the resulting surface tension  $F_H$  force module operating along the liquid contact border with the capillary surface.

Calculations were made for the following materials:

- ceramic microsphere having diameter of 100  $\mu\text{m}$ , density of 0.4  $\text{g}/\text{cm}^3$ ;
- iron powder monolayer with particle size of 30  $\mu\text{m}$ .

$F_T$  – sludge gravity (Fig. 2.3 b) depends on the sorbent, OP, water mass, and specific gravity. In calculations the quantity of water can be accepted, which is being held at the microsphere pores to 5–8 %, but the oil absorbent capacity – up to 30 % of the sorbent weight.

## 2.2. Impact of the Magnetic Field on Fine-Dispersed Particles in Water

The method for water decontamination from OP by means of ferromagnetic sorbents is based on interaction of the magnetic field with fine-dispersed particles possessing magnetic properties [106]. Iron and iron containing materials comprising nickel and cobalt are the most interesting. Under the impact of the magnetic field magnetization  $J$  is carried out in the magnetic material, characterised by material amount of magnetic moment  $M/V$ . Magnetization of magnetic material at certain intensity of known magnetic field tension  $H_E$  reaches the highest value  $J_E$ , which does not change at further increase of the field tension. This value is called a saturation magnetization. For iron it constitutes  $1.27 \cdot 10^6$  A/m [107]. This can be achieved with large magnetic field induction values. For iron it constitutes approximately 2.15 T<sub>L</sub>, but for nickel – only 0.61 T<sub>L</sub> [108].

It should be stressed that the properties of magnetic materials such as, for example, saturation magnetization, magnetic permeability, magnetic energy, etc., mainly depend on the material crystalline structure. Therefore, the use of nickel containing steel waste as basis for the sorbent is preferred, but copper or phosphorus in the content of sorbent have no impact on the sorption process.

If electromagnetic field operates with tension  $Ht$ , magnetization of the material reaches its volume of  $J_n$ , but then changes depending on the relaxation time  $k$ .

$$J_n = J_\infty(1 - e^{-t/k}), \quad (2.2)$$

where  $J_\infty$  is material magnetization at  $t = \infty$ ; and  $k$  is relaxation time.

Technically pure iron is a magnetic material with the highest saturation magnetization. Therefore, it is the most preferable to be used for the sorbent manufacturing.

Another important parameter influencing sorption process of the ferromagnetic sorbent is its magnetic permeability  $\mu$ . It indicates how many times the magnetic field induction in the environment B (that is, sorbent on OP surface) is different from the external magnetized field  $B_0$ .

It is high content of carbon, oxygen and sulphur, which reduces  $\mu$  the most. Therefore, extended storage of a sorbent will cause its quality deterioration and reduction of its sorption efficiency. Use of steel with *high carbon content* as ferromagnetic sorbent is not practical as well.

Holding of sludge on the water-oil surface is taking place on the account of environmental surface tension forces (in this case, as water-oil film), as well as due to air pillow present in the sorbent particle pores. As the sludge rises due to the film surface carving, Fa value decreases. Fa value, in calculation of the required capacity of the magnet power, may be taken into account in the form of coefficient 1.1–1.2.

The upward thrust value of electromagnet  $F_m$  is determined by formula

$$F_m = 4\pi \left( \frac{nI\mu\alpha}{cL} \right)^2, \quad (2.3)$$

where

- $n$  number of the electromagnet windings;
- $I$  current in winding;
- $\mu$  magnetic permeability of the environment;
- $\alpha$  magnetic thickness;
- $L$  circuit perimeter;
- $c$  the speed of light.

### 3. METHODOLOGICAL PART

#### 3.1. Experimental Research Methodology, Methods and Equipment

*Size of the particles* was determined by means of the light microscopy method with the *Biolam 70-R* microscope. Investigation of the powder fraction composition was carried out with the device in accordance with methodology [109]. Fluidity of dry powders and mixtures was assessed according to methodology at the device, as shown in Fig. 3.1.

Scanning electron microscope (SEM) *Zeiss EVO MA-15* with high resolution and the reflected electron detector (BSE) was used for examination of the particle surface morphology.

Experimental work was carried out with powdered materials having particle size between 10 and 200  $\mu\text{m}$ . Therefore, a variety of equipment was used for examination of the properties of powders as such, and the produced mixtures, as well as sludge containing ferromagnetic powder, water and oil products. Properties such as the particle bulk weight, size and shape, fluidity of powdered materials, binding capacity in regard to oil products, water absorption, buoyancy, etc. was first established.



Fig. 3.1. Powder fluidity evaluation device.

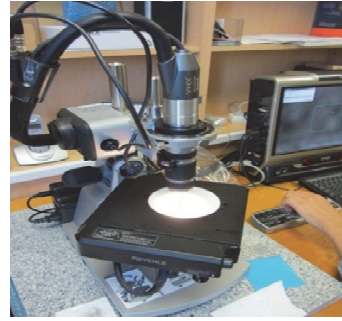


Fig. 3.2. Microscope VHX-2000: Keyence REMAX.

The volume meter was used in order to assess bulk weight [110]. Conical graduated plastic test-tube was weighed, the volume of which is  $1.5 \text{ cm}^3$ , it was placed in  $1 \text{ cm}^3$  of the substances to be studied, and the weight of test-tube with the substance was determined. Bulk weight of the substance was calculated as the weight difference between the test-tube with the substance and the test-tube itself. Weighing has taken place on the *Ohaus* analytical balances with accuracy of measurement  $0.1 \text{ mg}$ , and secondary electron detector (SE) [111]. The black and white images have been obtained by means of computer and analyzed in the *Image Pro 7* image analysis system (*Media Cybernetics*) [112]. EDS, equipped with *INCA Energy 350*, was used to assess the CS morphology and structure.

*Surface of cryogenic fracture* was used in order to capture the scanning electron micrographic. The *Keyence* corporation optical microscope VHX-2000 with VH-Z20R/W and VH-Z500R/W lenses was used for optical creation of images (Fig. 3.2) [113].

Thermal analysis equipment STA 449F1 *Jupiter* of firm “NETZSCH-Gerätebau GmbH” (Germany) [114] was used for *thermogravimetric research*.


*XRD measurements* were made using *Rigaku Ultima+* diffractometer with  $\text{Cu K}\alpha$  irradiation. Identification of the crystalline phase was implemented by means of the database of International Centre for Diffraction Data (ICDD) and *Sleve+2008* software [115].

*Specific surface of the powders* was determined by means of the “Beckman Coulter, Inc.” (U.S.) analyser SA 3100 [125].

*Powder spraying* was carried out with the newly developed equipment [117] (Fig. 3.3).



a)

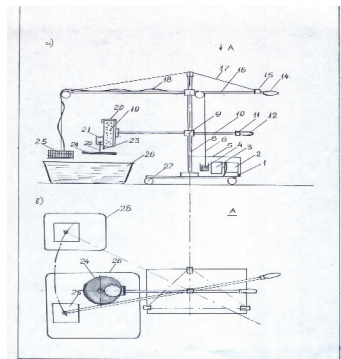

b)

Fig. 3.3. Experimental device for spraying of powdered sorbent and for collecting sludge by means of electromagnet: (a) overview; and (b) scheme.

The device (Fig. 3.3) consists of mobile platform *1*, where an electric motor *2* is installed with a reducer *3* and a winch *4*. An electromagnet lifting drive *25* is covered with housing *5*, electromagnet hanged up in a steel wire *6*. A vertical stanchion *8* is also fitted on the platform *1*, on which a horizontal bar *10* by means of a socket *9* is fixed with a powder spraying unit. The powder is placed in a tank *19* with *23* and cap *20*, on the tank *19* wall electric motor *21* with spindle *22* and disk *24* is mounted. Electromagnet *25* rotation control is implemented with handle *14* located on the horizontal bar *16*. The tank (Fig. 3.4 a)) capacity is 2 litres. By means of drive the disc *24* rotates at a speed of 2000 rpm, which allows to perform powder spraying with speed 2–2.5 m/min.

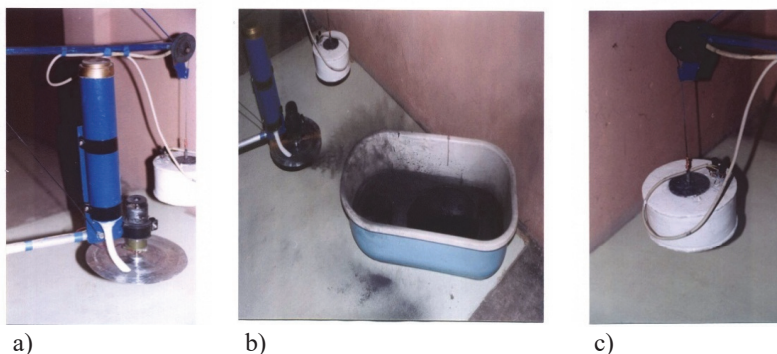


Fig. 3.4. Experimental equipment units: a) spraying mechanism; b) bath; and c) electromagnetic coil for sludge lifting by means of flexible wire cable.

Electromagnet lowering to the water surface takes place via drive by electric motor. Movement of electromagnet in the horizontal plane of work area is taking place through lever *16* and handle *15*. Flat type electromagnet is weighing 4 kg. It is twisted from the copper wire with a diameter of 1.2 mm. When delivering 4 A power supply to the winding, its carrying capacity reaches 0.3 kg, but at 6A power – 7.5 kg.

Crushing of the materials is used for *manufacturing of sorbents* with high speed disintegrator (12000 rev.<sup>-1</sup>) [128], mixing powders and emulsion preparation by means of dispersant [116]. *Collection of the sorbent with captured OPs* is implemented by means of magnetic [118] and electromagnetic equipment [120], which was developed anew.

Determination of *water absorption of sorbents and raw materials* was carried out in accordance with the methodology in a plastic test-tube, the volume of which is 5 cm<sup>3</sup>, 500 mg of the original substance and a sorbent was inserted, test-tubes weighed and 4 ml water added. Test-tubes containing the substance or the sorbent and water were placed in a mechanical shaker or incubated for 30 minutes. Water was drained from the test-tubes through thick paper filter and the test-tube weight was determined together with sorbent after contact with water. Calculations were made on the basis of water absorption ratio between the original material and the sorbent obtained on its basis.

The *sorbent binding capacity* in relation to oil products was established in accordance with the methodology [16]. The amount of 30 cm<sup>3</sup> of water and 1 cm<sup>3</sup> of oil was poured into a previously weighed Petri plastic container, the volume of which was 50 cm<sup>3</sup>. Weight of sorbent as 50 mg or 100 mg was taken, and the sorbent was imposed from the top onto the oil slick, and mixed, by gently shaking for 5 minutes, and the collected mixture was removed from the surface. The completeness of removal was assessed either visually or by weighing.

*Kinetic persistence* in disperse systems (ability of a disperse system to retain uniform particle layout along the entire environmental capacity volume) is described by Stokes' law [129]:

$$V_s = \frac{2}{9} \frac{r^2 g (\rho_p - \rho_f)}{\mu}, \quad (3.1)$$

where

- $V_s$  stabilised particle velocity (m/s) (particle moves downwards if  $\rho_p > \rho_f$  and upwards if  $\rho_p < \rho_f$ );
- $r$  Stokes' radius of the particle, m;
- $g$  gravitational acceleration, m/s<sup>2</sup>;
- $\rho_p$  density of the particles, kg/m<sup>3</sup>;
- $\rho_f$  fluid density, kg/m<sup>3</sup>;
- $\mu$  fluid dynamic viscosity, Pa·s.

On the basis of Stokes' formula (3.2), sedimentation (segregation) speed is directly proportional to the speed of squared difference between the radius of particles, phase and the environmental density, as well as inversely proportional to the environmental viscosity.

The *volume occupied by inter-particle gaps* is calculated according to formula

$$\mu' = \frac{V_{par}^{total} \cdot (V_{kop}^{solut} - V_{skid})}{V_{par}} \cdot 100\%, \quad (3.2)$$

where

- $V_{par}$  is free bulk sample volume, ml;
- $V_{total}$  is mixture (sample + liquid) volume, ml;
- $V_{solut}$  is volume of the starch solution, ml.

*Magnetization of the materials* was taking place by means of magnetization device (Fig. 3.5). *Magnetization of the material* was evaluated by Gaussmeter (Fig. 3.6).



Fig 3.5. Magnetization device.



Fig. 3.6. Gauss/Tesla Meter FH-55, MAGNET-PHYSIK Dr. Steingroever GmbH.

### 3.2. Materials Used for the Research

Iron powders, shred metal particles of rolling mill scale and certain other metallurgical industry waste was used for manufacturing of the sorbents with ferromagnetic properties as original powder-based materials. For example, the author has selected the following brands of metal powders: ASC 100.29 – sprayed, used in the manufacture of structural parts with powder metallurgy techniques; MH 80.23 – restored porous, used in the manufacture of self-lubricating plain shaft bearings; M20/80-19 with a low carbon content and R-12 with reduced hydrogen content used in the manufacture of friction products. All the powders are produced by the

company *Höganäs AB* (Sweden) [79]. Powders, such as ПЖРВ [PZRV] were used as well, which were sprayed with air and produced by *ООО “ССМ-Тяжмаш”* [SSM-Tyazmash Ltd] (Russia) [126], ПЖР [PZR] 3.315.26 -30, sprayed with water and produced by КЗПМ [KZPM] (Ukraine) [127]. An opportunity to use RTUS-1 brand of rolling mill scale of Liepaja Metallurgical Plant as the sorbent was studied as well.

#### 4. CREATION OF COMPOSITE FERROMAGNETIC SORBENT (EXPERIMENTAL PART)

When working on the topic “Ferromagnetic Sorbents and their Potential for Collecting Pollution with Spilled Oil Products”, much attention was paid to experimental work, which covered the ferromagnetic sorbent manufacturing and operational phases, as well as their reuse and recovery capabilities.

Topicality of the creation of composite powdered ferromagnetic sorbent with typical KFMS magnetic properties is highlighted in many patent studies, especially in [131]–[133]. The authors have used different bases, which were saturated with fine-dispersed (ferromagnetic) particles. In this direction Riga Technical University has commenced the studies also with *fine-sprayed* iron powders [17]. Common disadvantage of the previous studies is high proportion of sorbent particles causing their poor buoyancy.

This Thesis offers a new technology for production of composite ferromagnetic sorbent (CFS) [134], which includes the preparation of hollow ceramic material cenosphere (CSP) base, then modifying thereof, by applying ferromagnetic powder and adding light products that increase buoyancy and sorption capacity.

This Thesis has studied commercially available ways of four cenospheres, their origin (field and thermoelectric power plant) shown in Table 4.1.

Table 4.1

**Designation, Source of Origin and Granulometry of the Used CSF**

<i>Sample description</i>	<i>Coal deposit</i>	<i>TPP</i>	<i>Granulometry, <math>\mu\text{m}</math></i>
CSF1	Kuznetskoe	Troitskaya	250–500
CSF2	Kuznetskoe	Troitskaya	56–100
CSF3	Kuznetskoe	Troitskaya	150–250
CSF4	Ekibastuz	Tomusinskaya	0–500

As you can see, the samples CSF1-CSF3 have come from the same coal deposit and TPP, where CSF is formed in the carbon incineration process, only the granulometric composition and the delivery price differs. However, several characteristics must be determined, because incineration modes may vary, there may also be inaccuracies in the raw material data provided by the supplier.

As it has already been stated in the theoretical part of the paper – cenospheres are hollow, spherical objects with a smooth surface. Cenospheres, which were used in this Thesis, also have the above mentioned properties clearly visible in the images obtained with optical (Fig. 4.1) and SEM microscope (Fig. 4.2).



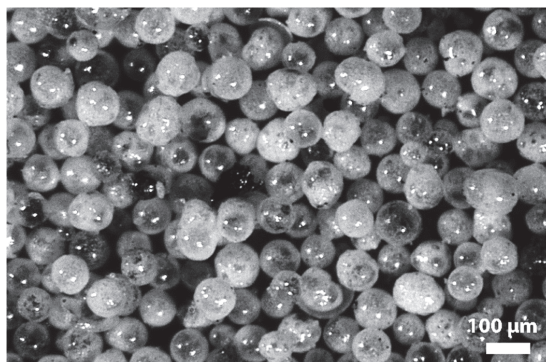


Fig. 4.1. Sample photomicrography obtained with optical microscope CSF2.

More than 15 optical microscopy images were made for each sample. The most typical of those are shown in Fig. 4.2. Upon their analysis it can be concluded that almost all particles of sample CSF2 have a correct spherical shape practically free of inclusions, their appearance is homogeneous, unlike of the samples CSF1, CSF3 and CSF4.

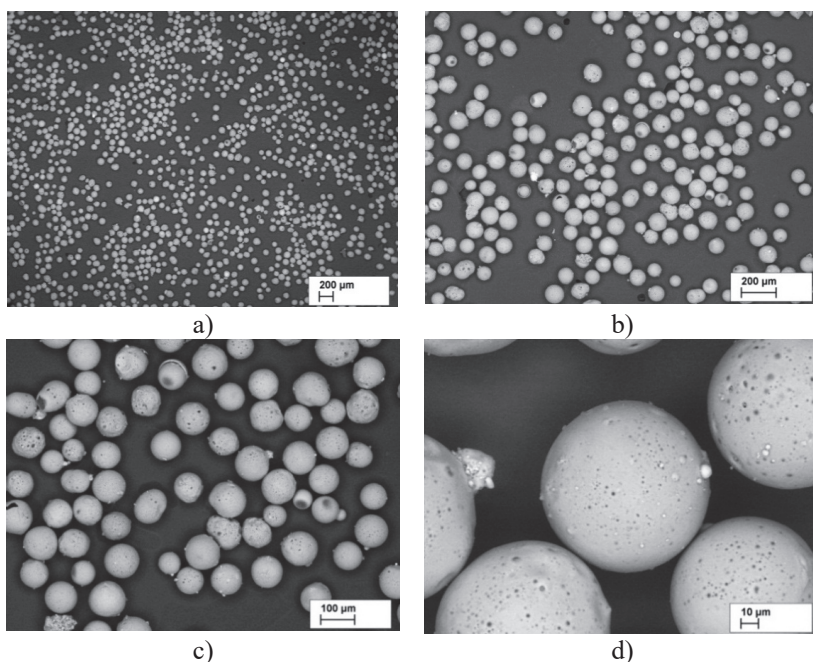


Fig. 4.2. SEM images of CSF2 microsphere with enlargement of a) 20x; b) 50x; c) 100x; and d) 500x .

Sample CS1 presents objects, which have very different transparency and colour – they have transparent, semi-transparent, and opaque (white) cenospheres. The degree of transparency is likely dependent on the cenosphere wall thickness and its construction. Sample CSF3 has typical black inclusions (possibly incompletely burnt coal). Small balls CSF4 were found in the sample with size more than 500 µm, which was later confirmed in granulometry analysis.

Composite sorbent (KS) was made in a special mixer – reaction chamber (Fig. 4.3). Continuous rotation of an obliquely installed cylinder was taking place with a speed of 300–500 rpm.

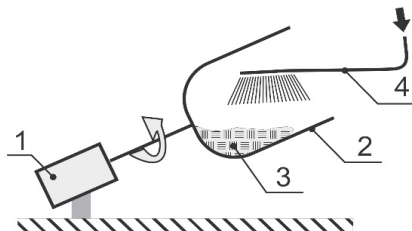


Fig. 4.3. Scheme of installation of KS production:  
1 – motor, 2 – cylinder, 3 – material to be processed, 4 – binder delivery.

Microspheres, particles of ferromagnetic material, components increasing the specific surface (for example, aluminium flakes and / or peat particles) are supplied in certain proportions to the reaction chamber (rotating cylinder). During collision of binders, as well as during further ball production process, the particles mutually agglutinate, creating KS. Binder hardening is attained through heating. Separation of the finished product is further performed from raw material components with magnet and gravity separators. In addition, the sorbent may be treated with hydrofobising composition.

Composite sorbents *Comsor*, *Comsor-125*, and *Comsor-M* are developed in cooperation between Riga Technical University and Rezekne Academy of Technologies. The technology of obtaining is described in Patent P-12-205 on 28 December 2012 [2].

The scheme of the KFS manufacturing process is shown in Fig. 4.4.

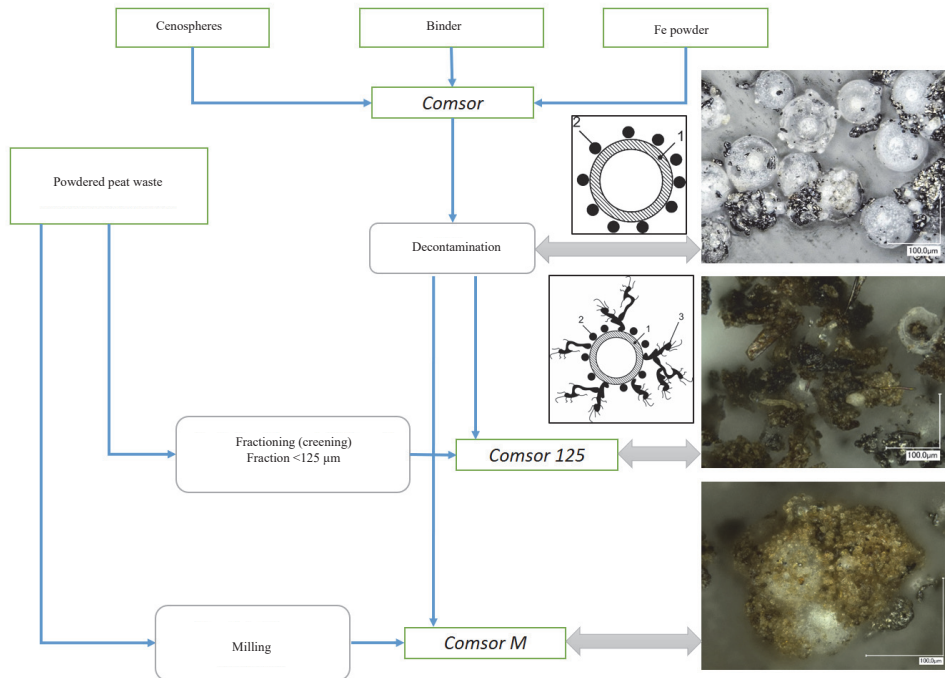


Fig. 4.4. The scheme for obtaining composite sorbent *Comsor*, *Comsor-125*, *Comsor-M*, and KFS *Comsor* morphology with varied enlargement.

KFS microstructure is displayed in Fig. 4.5.

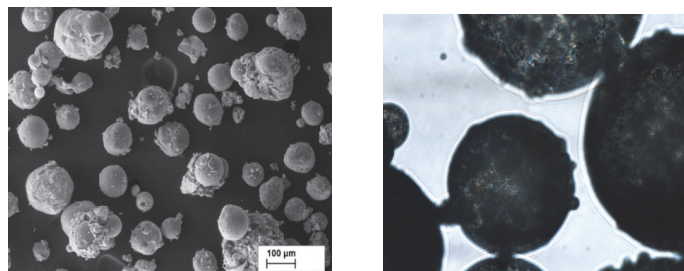


Fig. 4.5. KFS Comsor with varied enlargement.

Heating contributes to the binder hardening. Separation of the finished product from raw material components is carried out with a magnet and gravity separators.

KFS *Comsor-125* is made of KFS *Comsor*, for maximizing specific surface of the component, peat particles are used having passed through 125  $\mu$  large apertures.

KFS *Comsor-M* is produced in a similar manner. Maximising component of its specific surface – peat particles, ground in ball mills, are fed to the reactor chamber in certain proportions.

Oil sorption test results for the obtained KFS are as follows: *Comsor* –  $1.32 \pm 0.12$ ; *Comsor-125* –  $1.87 \pm 0.18$ ; *Comsor-M* –  $1.53 \pm 0.11$  (g/g). These data are well correlated with the particle morphology in accordance with the experimental data, according to which it is determined.

*Comsor-125* can receive for 42 weight% and *Comsor-M* – for 16 weight% more oil than *Comsor*. Upon the analysis of sorbent activity, it is possible to claim that oil / petroleum is staying in the improved / enhanced / developed CFSs due to two reasons:

- 1) owing to peat particles with increased specific surface area of the sorbents;
- 2) due to filling of gaps between the sorbent particles.

Large increase in oil absorption for *Comsor-125* absorbent may be explained by hypothesis. Spherical objects in ideal circumstances may be arranged in four structural ways. The following arrangements may have different channels between particles that can be filled by liquids in the case of good moistening capacity.

## 5. NOVELTY OF THE THESIS

### Scientific novelty of the Thesis

- New methodology developed for creation of new types of sorbents with ferromagnetic properties for sorption of oil products.
- A process model proposed for sorption of oil product films from water surface by means of ferromagnetic particles.
- Analysis provided regarding the impact of composition and properties of ferromagnetic sorbents on the sorption process.
- New methods offered for production of composite sorbents with ferromagnetic properties.
- New methods proposed for sorbent spraying and sludge removal from water by means of magnetic and electromagnetic devices.
- Data obtained for thermogravimetric and differential thermal analysis of iron powder-base sorbent and the collected sludge in the temperature range up to 1000 degrees.
- Proposal for use of the collected OPS (oil product sludge) as high temperature fuel product.

### Practical novelty of the research

- Some new composite sorbents (*Comsor 125*, *Comsor M*, etc.) developed with magnetic properties.
- New types of ferromagnetic sorbents developed on the basis of use of technological residues and natural raw materials.
- Stands developed, designed and tested for spraying sorbents on the water surface contaminated with oil products for study of the processes.
- Stands developed, designed and tested for collection of the sludge by means of magnetic and electromagnetic equipment.
- New sorbent recovery and reuse technology proposed.
- New ways for the use of sludge proposed, sorbents obtained with oil products (for concrete cutting with gas flame, production of fuel emulsions and copper extraction from solutions).

## 6. CONCLUSIONS

1. Upon examination of various methods and technologies to treat oil spills in the water by means of different sorbents, it was concluded that the powdered ferromagnetic sorbents (PFSs) are prospectively usable, which is explained by their non-toxicity, the possibility to apply new, rapidly developing treatment methods by means of magnetic fields, and recovery capabilities, as well as effective disposal techniques. Moreover, the PFSs were still little explored until now.
2. New types of composite ferromagnetic sorbents (*Comsor*) have been developed, which are based on the use of hollow microspheres (cenospheres) to surface of which ferromagnetic particles and extended fibres are attached. *Comsor* KPSs, in comparison with other iron powder-based FMSs, have shown their sorption increase by 5–7 %, while for buoyancy – more than ten times.
3. Iron powder crushing technology has been applied to production of KPS fine ferromagnetic particles by means of high speed impact action disintegrator. The selective crushing method has proved to be the most effective one.
4. A method has been developed for treatment of water from oils by means of electromagnetic device. The required dependence of the field voltage from the height of placement of the device above the polluted surface has been established. Use of the electromagnetic device has been demonstrated for lifting of sludge up from 1 m in depth.
5. The improvement potential of FMSs has been shown by means of processing and subsequent drying of the sorbent. It is also reasonable to assume that the sorbent can be reused. In addition, high speed impact action disintegrator was first used in the manufacture of ferromagnetic emulsions.
6. Sorption processes have been analysed by means of FMSs. The effect of shape and size of the particles is indicated. It has been determined that powders with a particle size of 20–40  $\mu\text{m}$  with enlarged specific surface can be used in the most efficient way.
7. Sludge thermogravimetric research in the temperature range from 20 to 1000 °C has allowed to clarify certain important stages – below 150 °C, intense surface evaporation of water from the surface of iron particles is taking place, above 300 °C – evaporation of water from the particle capillaries. At the beginning the weight of powder decreases, however, the oxidation process results in almost 40 % increase. Sorption capacity of a sorbent together with oil amounts to 8 % of water on average. Sorption capacity of metal powder is amounting to 20–22 % on average. Processing of the used sorbents requires temperature of not less than 600 °C. Safe products  $\text{H}_2\text{O}$ ,  $\text{CO}^2$  are released during processing.

8. The technology has been developed and tested using the mill scale and the collected FMS for cutting of concrete.
9. Technology and equipment has been developed by means of the mill scale with FMS, for copper extraction from the solution.
10. Innovativeness of the research has been approved by two Latvian patents (see Annex).

## ABBREVIATIONS AND SYMBOLS USED IN THE THESIS

**OP** – oil product  
**SOP**– spilled oil product  
**MRM** – metallurgical residual materials  
**MRCC** – liquidation of the consequences of oil accidents  
**OPC** – oil pollution case  
**FSS** – fuel service station  
**FS** – ferromagnetic sorbent  
**CS** – composite sorbent  
**DS** – hollow sphere  
**MSp** – minisphere  
**McSp** – microsphere  
**PU** – polyurethane  
**PS** – polystyrene  
**PVC** – polyvinyl chloride  
**Bd** – bulk density  
**SEM** – scanning electron microscope  
**OM** – optical microscope  
**LAD** – high speed disintegrator  
**PIE** – powder spraying equipment  
**XPS** – X-ray photoelectronic spectroscopy  
**AFM** – atomic force microscopy  
**TGP** – thermogravimetry studies  
**DTA** – differential thermal analysis  
**Ab** – absorption  
**Ad** – adsorption  
 $\gamma$  – surface energy

## BIBLIOGRAPHY

1. Oil-in-Water Content Monitor Development Program Summary. US Coast Guard, Dec. 1975.
2. Гольдберг В.М., Зверев В.П., Арбузов А.И., Казеннов С.М. и др. Техногенное загрязнение природных вод углеводородами и его экологические последствия. М.: Недра, 2001., 150 с.
3. Нунупаров С.М. Предотвращение загрязнений моря судами. М.: Транспорт, 1979.
4. Демина Л.А. О ликвидации нефтяных загрязнений // Энергия. 2000. N.10. С. 51-54.
5. Красавин А.П., Весни Н.М. Проблемы борьбы с аварийными разливами нефти и нефтепродуктов. Топливо-энергетический комплекс. N.3, 2000, с. 102-103.
6. Fontanals N Marcé., R. Maria, Borrull F. Overview of the novel sorbents available in solid-phase extraction to improve the capacity and selectivity of analytical determinations. Contributions to science, 6 (2): 199–213 (2010), Barcelona. Spain. DOI: 10.2436/20.7010.01.97 ISSN: 1575-6343.
7. Mahmoud M.E., Abdel-Fattah T.M., Osman M.M, Ahmed S.B. Chemically and biologically modified activated carbon sorbents for the removal of lead ions from aqueous media. J Environ Sci Health A Tox Hazard Subst Environ Eng. 2012;47(1):130-41. doi: 10.1080/10934529.2012.630292.
8. Sorbents and biological products. Iegūts no: <http://www.econad.com.ua>.
9. Porous magnetic sorbent. Patent RU Nr. 2241537. iegūts no: <https://patents.google.com/patent/WO2012174616A1/en>
10. Gleich B., Weizenecker J. Tomographic imaging using the nonlinear response of magnetic particles. Nature, 435 (2005), pp. 1214-1217.
11. Marine environment. Iegūts no: <http://www.amsa.gov.au/environment/index.asp>.
12. Spill Response & Absorbents. Iegūts no: <http://www.oiltechnics.com/products/industrial-cleaning/oil-decontamination/oil-spill-clean-up/spill-magnet>
13. Laurent S., Forge D., Port M., Roch A., Robic C., Vander Elst L., Muller .N.R. Magnetic iron oxide nanoparticles: synthesis, stabilization, vectorization, physicochemical characterizations and biological applications. Chem. Rev., 108 (2008), pp. 2064-2110/.
14. Caine M., Dyer G., Holder J.V. The Use of Clays as Sorbents and Catalysts. Natural Microporous Materials in Environmental Technology. Pp. 49-69.
15. Jauna veida metālpulveru izstrādāšana un to efektīva izmantošana būvniecībā un vides aizsardzībā. RTU, IZM TOP projekts 6371/99 (vad. Prof. V.Mironovs).
16. Поляков А.А. Утилизация отходов нефтепродуктов CORVUS Company. Iegūts no: [http://www.corvus.lv/files/pdf/2\\_Recycling\\_of\\_waste\\_oil.pdf](http://www.corvus.lv/files/pdf/2_Recycling_of_waste_oil.pdf).
17. Миронов В.А. Новые области применения железных порошков. 3 межд. конф. Материалы и покрытия в экстремальных условиях. Крым, Украина, 2004, с. 530-531.
18. Способ очистки сточных вод, содержащих эмульгированные нефтепродукты. Patents RU Nr. 2156225. Iegūts no: <http://bd.patent.su/2156000-2156999/pat/serv1/servletbbde.html>
19. Сорбент для очистки воды от углеводородов, способ его получения и способ очистки воды. Patents RU Nr. 2088534. Iegūts no: <http://www.freepatent.ru/patents/2232633>
20. Порошкообразный магнитный сорбент для сбора нефти, масел и других углеводородов. Patents RU Nr. 2462303. Iegūts no: <http://www.freepatent.ru/patents/2462303>

21. Matar S., Hatch L.F. (2001). *Chemistry of Petrochemical Processes*. Gulf Professional Publishing. ISBN 0-88415-315-0.
22. Инчукалнс - город на гудроне. Iegūts no: [www.d-pils.lv/news/2/281593](http://www.d-pils.lv/news/2/281593)
23. Товарные нефтепродукты, их свойства и применение. Справочник под ред. Н.Г. Пучкова, М., 1971.
24. Нефтепродукты. Справочник под ред. Б.В. Лосикова, М., 1966.
25. ISO 3448-75. Смазочные материалы индустриальные. Классификация вязкости. Iegūts no: <http://www.newchemistry.ru/masla.php?ID=25>
26. Юрченко А.А., Поляков А.А. Сернокислые гудроновые озера и методы их утилизации. Iegūts no: [www.corvus.lv/files/pdf/3\\_Sulfuric\\_tar\\_lakes.pdf](http://www.corvus.lv/files/pdf/3_Sulfuric_tar_lakes.pdf)
27. Prasad M.S., Kumari K. (1987). Toxicity of Crude Oil to the Survival of the Fresh Water Fish *Puntius sophore* (HAM.). *Acta Hydrochimica et Hydrobiologica*. 15: 29. doi:10.1002/aheh.19870150106
28. Влияние нефти и нефтепродуктов на окружающую среду. Iegūts no: <http://www.activestudy.info/vliyanie-nefti-i-nefteproduktov-na-okruzhayushhuyu-sredu>
29. Магеррамов А.М. и др. Удаление тонких нефтяных пленок с водной поверхности. Молодой ученый. №7. Т.1. 2011. с. 65-68.
30. Набаткин А.Н., Хлебников В.Н. Применение сорбентов для ликвидации нефтяных разливов. Нефтяное хозяйство. 2000. № 11. с. 61.
31. Самойлов Н.А., Хлесткин Р.Н., Шеметов А.В., Шаммазов А.А. Сорбционный метод ликвидации аварийных разливов нефти и нефтепродуктов. М.: Химия, 2001. 189 с.
32. Novīks G. *Ekotehnoloģijas pamati*. RA: Rāzekne, 2002, 243 lpp.
33. Гвоздииков В.К., Захаров В.М. Технические средства ликвидации разливов нефтепродуктов на морях, реках и водоемах. Ростов-на-Дону, 1996, 256 с.
34. Bonovie Zagragdeniya. Iegūts no: [http://www.tzik.ru/articles/bonovie\\_zagragdeniya.html](http://www.tzik.ru/articles/bonovie_zagragdeniya.html)
35. Amin J.S., Abkenar M.V., Zendejboudi S. Natural sorbent for oil spill cleanup from water surface: environmental implication. *Ind. Eng. Chem. Res.*, 2015, 54 (43), pp 10615–10621. DOI: 10.1021/acs.iecr.5b01715.
36. Avārijas Seku likvidācijas resursi. Iegūts no: [www.mrcc.lv](http://www.mrcc.lv).
37. Oil skimmers. Iegūts no: [https://www.vikoma.com/Oil\\_spill\\_solutions.html](https://www.vikoma.com/Oil_spill_solutions.html).
38. Sulphonated and Oxidised Indene Polymers and Their Use as Dispersents. Patent No WO /1995/004088. Iegūts no: <https://patentscope.wipo.int/search/en/detail.jsf?docId=WO1995004088>
39. Применение диспергентов для обработки нефтяных разливов. Iegūts no: [http://www.itopf.com/uploads/translated/TIP\\_4\\_2011\\_RU\\_Use\\_of\\_dispersants\\_to\\_treat\\_oil\\_spills.pdf](http://www.itopf.com/uploads/translated/TIP_4_2011_RU_Use_of_dispersants_to_treat_oil_spills.pdf)
40. Jūras un upju krasta erozijas monitorings. Iegūts no: <http://www.metrum.lv/lv/kur-stradajam/vide/udens/juras-un-upju-krasta-erozijas-monitorings/>
41. Ar naftas produktiem piesārņotas grunts attīrīšanā izmanto inovatīvu. Iegūts no: [www.lnk.lv/lv\\_LV/posts/26](http://www.lnk.lv/lv_LV/posts/26), 2013.
42. Hawrot M., Nowak A.. Effects of Different Soil Treatments on Diesel Fuel Biodegradation *Polish J. of Environ. Stud.* Vol. 15, No. 4 (2006), 643-646
43. Утилизация нефти и мусора. Iegūts no: [www.itopf.com/.../TIP\\_9\\_2011\\_RU\\_Disposal\\_of\\_oil\\_and\\_debris.pdf](http://www.itopf.com/.../TIP_9_2011_RU_Disposal_of_oil_and_debris.pdf)
44. Vane, C.H. et al. Biodegradation of Oak (*Quercus alba*): A Molecular Approach. *Journal of Agricultural and Food Chemistry*. (2003). 51 (4): 947–956. PMID 12568554. doi:10.1021/jf020932h.
45. Ancheyta J. Deactivation of Heavy Oil Hydroprocessing Catalysts: Fundamentals and Modeling. 2016. 336 p. ISBN: 978-1-118-76984-3



46. Li D., Berruti F., Briens C. Autothermal fast pyrolysis of birch bark with partial oxidation in a fluidized bed reactor. *Fuel*, Volume 121, 1. 2014, P. 27–38.
47. Putsche M., Scahill V. Large-Scale Pyrolysis Oil Production: A Technology Assessment and Economic Analysis. NREL/TP-510-37779; National Renewable Energy Laboratory (NREL), (2006) Golden, CO.
48. Факел-1М установка для сжигания нефтешлама и нефтепродуктов. Iegūts no: <http://eko-log.ru/node/313>
49. A/s “B.L.B. Baltijas Termināls” naftas ķīmijas rajona grunts un gruntsūdeņu piesārņojums. Ekoloģiskās izpētes darbu atskaite. R.: SIA “ATW”, 1995.
50. Пономарев В.Г., Иоакимис Э.Г., Монгайт И.Л. Очистка сточных вод нефтеперерабатывающих заводов. М.: Химия, 1985. 256 с.
51. Кулубова Л.И., Морозов С.В. Очистка нефтесодержащих сточных вод: Аналит. обзор. СО РАН. ГПНТБ, НИОХ. Новосибирск, 1992. 72 с.
52. Мочаров В.М., Савицкая П.В., Егорова О.А.др. Способ очистки вод от нефтепродуктов и масел. А.с. 1451099 СССР, МКИ С 02 F 1/28.
53. Сенин А.Н., Горчаков В.Д., Денисова М.В. и др. Способ концентрирования нефтепродуктов из водных сред. А.с. 1444307 СССР, МКИ С 02 F 1/28, G 01 N30/08.
54. Беличенко Ю.П., Береза А.П., Рудин Т.Р. и др. Способ очистки сточных вод. А.с. 1452550 СССР, В 01 D 35/06; В 03 С 1/00.
55. Павлик П.Е., Бочманов А.Д. Сорбент для сбора нефти и нефтепродуктов с поверхности воды. 14-й Менделеевский съезд по общей и прикладной химии. Т.2. М., 1989. С. 444.
56. Sandberg Fr.H. Petroleum product absorption method and apparatus. Пат. 4784773 США, МКИ С 02 F 1/40.
57. Тимошенко М.Н., Клеменко Н.А. Применение активных углей в технологии очистки воды и сточных вод. *Химия и технология воды*. 1990. т.12., № 8. с. 727-738.
58. Adsorption system. *Water Eng. and Manag.* 1989. Vol. 136. N9. P. 61.
59. Румянцев В.А., Левченко А.Б. Нефтяные разливы в Балтийском море. Iegūts no: <http://www.limno.org.ru/win/eco.htm>
60. Sludge Pumps Sulzer. Iegūts no: <https://www.sulzer.com/bg/Products-and-Services/Pumps-and-Systems/Dewatering-Pumps/Sludge-Pumps>.
61. Сорбент для очистки нефтесодержащих промышленных стоков и способ его получения. Patent RU. 971129/25. Iegūts no: <http://www.freepatent.ru/patents/971129/25>
62. Способ получения сорбента для очистки от нефти твердых и водных поверхностей. Patent RU 2116128. Iegūts no: <http://www.freepatent.ru/patents/2116128>
63. Сорбционно-активный материал для очистки воды от нефтепродуктов. Patent RU 2158177. Iegūts no: <http://bd.patent.su/2158000-2158999/pat/servl/servletce10.html>
64. Дсорбент для очистки от нефтепродуктов. Patent RU 2124397. Iegūts no: <http://ru-patent.info/21/20-24/2124397.html>
65. Способ комплексной переработки техногенных осадков. Patent RU 2057725. Iegūts no: <http://www.freepatent.ru/patents/2057725>
66. Valorisation of by-products of wastewater, sewage or sludge processing. Patent Y02W10/40.
67. Colin T., Bories A., Sire Y., Perrin R. Treatment and valorisation of winery wastewater by a new biophysical process. *Water Sci Technol.* 2005. 51(1). P. 99-106.

68. Мечковский С.А., Лесникович А.И., Воробьева С.А., Заневская Ю.В., Козыревская А.Л., Молоток Е.В. Высокодисперсные магнитоизвлекаемые сорбенты // Вестн. Белорус. Гос. Ун-та. Сер.2, 1998 №3. с. 13-16,
69. Ферромагнитный сорбент и устройство для сбора нефтепродуктов с водной поверхности. Ершов О. Л., Жигалин Г. Я., Блохин Д. Ю., Иванов П. К., Филиппов В. И., Махлин Р. С., Мошечков Н. Г.  
Iegūts no: <http://magneticliquid.narod.ru/authority/011.htm>
70. Исследование получения железорудного концентрата для очистки воды от нефти. Хотынюк С.С. Iegūts no: <http://kulibin.org/projects/show/3112/>
71. Миронов В. Новые области применения железных порошков. Труды 3-ей межд. конференции «Материалы и покрытия в экстремальных условиях». Крым, Украина, сент. 2004, с. 530-531.
72. Sorbent dlja nefteprodukta. Украинский химический журнал, 47. sējums, 1-6. izdevums, 1981.
73. Mironovs V., Lapkovskis V., Zemčenkovs V. Sorbents naftas produktu savākšanai. LVR patents LV 13927 B. 20.08.2009, Int. Cl. B01J20/02.
74. Shishkin A., Mironovs, V., Lapkovskis V. Ferromagnetic Sorbents For Collection and Utilization of Oil Products. 22nd Int. Baltic Conf. on Engineering Materials & Tribology (BALTMATRIB). Book Series: Key Engineering Materials. Volume: 604, 2014. pp. 122-125.
75. Способ очистки сточных вод, содержащих эмульгированные нефтепродукты. Patents RU 2156225.  
Iegūts no: <http://bd.patent.su/2156000-2156999/pat/servi/ servletbbde.html>
76. Dao HV, Ngeh LN, Bigger. The use of magnetic particle technology in the cleansing of oiled birds. Abstract, Proceedings (on a CD Rom) of the workshop on Improving Oiled Wildlife Preparedness and Response in Australia, Australian Maritime Safety Authority (AMSA), Australia. Brisbane, Australia, 18 February 2004.
77. Железные порошки. Iegūts no: <https://www.hoganas.com/ru-RU/products>.
78. Hibst H., Magn J. Materials. 74, 1988. pp. 193-202.
79. Khan M.K. (1980). The Importance of Powder Particle Size and Flow Behavior in the Production of P/M Parts for Soft Magnetic Applications. Intern. J. Powder Metallurgy and Powder Tech. 16 (2). P. 123–130.
80. Боброва З.М. и др. Применение отходов горно-металлургических и металлургических производств в целях рационального природопользования. Известия Уральского государственного горного университета, 2015, с.16-25.
81. Dimitrova S.V. (1996). Metal sorption on blast-furnace slag. Water Research. 30 (1): 228–232. doi:10.1016/0043-1354(95)00104-S.
82. KVV Liepājas metalurģis mēnesī saražo jau 26 tūkstošus tonnu.  
Iegūts no: [www.metalurģis.lv/?a=2&b=0&e=525](http://www.metalurģis.lv/?a=2&b=0&e=525)
83. Промывочный шлам. Iegūts no: <http://www.findpatent.ru/patent/240/ 2403294.html>
84. Qazi S.A., Qazi N.Sh. Natural Resource Conservation and Environment Management. APH Publishing. Retrieved, 12, 2016.
85. Летимин В.Н. и др. Пыль и шлам газоочисток металлургических заводов и анализ путей их утилизации. Теория и технология металлургического производства, 2015. с. 82-88.
86. SchEele J. Oxyfinestm technology for the re-melting of fines, dust and sludge. Proceedings: Tenth Intern. Ferroalloys Congress; 2004, pp. 678-686.
87. Mironovs V. Betona un dzelzsbetona griešanas metodes. Būvēt. Nr. 23, 2002, 44-45. lpp.
88. СВЧ ферриты и диэлектрики. Iegūts no: <http://www.magneton.ru/ cat.php?id=154>.

89. Шихтовой материал для изготовления стеклокерамики.  
Iegūts no: <http://www.findpatent.ru/patent/214/2142437.html>
90. Peng H.X., Fan Z., Evans J.R.G. Factors affecting the microstructure of a new ceramic foa. Vol. 26, 2000, pp. 887–895.
91. Colombo P., Scheffler M., Eds., Cellular Ceramics: Structure, Manufacturing, Properties and Applications// Weinheim: WILEY-VCH Verlag, 2005.
92. Montanaro L., Jorand O.Y., Fantozzib G., Negroa A. Ceramic Foams by Powder Processing// vol. 18, 1998, pp. 1339–1350.
93. Muhamad Nor M.A.A., Hong L.C., Arifin Ahmad Z., Md Akil H.. Preparation and characterization of ceramic foam produced via polymeric foam replication method// J. Mater. Process. Technol., vol. 207, no. 1–3, 2008. pp. 235–239.
94. Gianella S., Gaia D., Ortona A. High temperature applications of Si-SiC cellular ceramics// Adv. Eng. Mater., vol. 14, No. 12, 2012, pp. 1074–1081.
95. Brakšs N. Purvi un kūdra. Rīga: Latvijas PSR Zinātņu akadēmijas ķīmijas institūts. 1961. 92 lpp.
96. [rus.db.lv/ekonomika/.../latvijas-kij-torf-eksport-v-34-strany-62991](http://rus.db.lv/ekonomika/.../latvijas-kij-torf-eksport-v-34-strany-62991)
97. Kūdras produkti. Iegūts no: [www.laflora.lv/lv/kudras\\_produkti/](http://www.laflora.lv/lv/kudras_produkti/)
98. Физико-химические свойства сапропелей. Iegūts no: <http://www.activestudy.info/fiziko-ximicheskie-svoystva-sapropelej/>
99. Šiškins A., Mironovs V., Treijs J. Feromagnētiskais sorbents. Latvijas Republikas patents Nr. LV 14820 B 20.06.2014.
100. Грег С., Синг К. Адсорбция, удельная поверхность, пористость. М.: Мир, 1984. 310 с.
101. Фролов Ю.Г. Курс коллоидной химии. М.: Химия, 1988, 464 с. ISBN 5-7245-0244-5.
102. Veprikova E.V., Tereshchenko E.A., Chesnokov N.V., Shchipko M.L., Kuznetsov B.N. Peculiarity of Water Purifying from Oil Products with Make Use of Oil Sorbents, Filtering Materials and Active Coals. SFU: Krasnojarsk. ISSN: 1998-2836 , T.3, N.3, 2010. с. 285-304.
103. Квашева Е.А., Ушаков А.Г., Ушакова Е.С., Козлова И.В. Магнитоуправляемый сорбент «Магнесорб» на основе вторичного сырья // Научно-методический электронный журнал «Концепт». 2016. Т. 26. С. 996–1000. Iegūts no: <http://e-koncept.ru/2016/76302.htm>
104. Мишин Д.Д. Магнитные материалы. М.: Высш. школа, 1981. 335 с.
105. Хек К. Магнитные материалы и их техническое применение. М., 1973.
106. Bruce B.W. What Is Particle Size Distribution Weighting. Brookhaven Instruments Corporation, 2011, pp.1–4.
107. Metallic powders. Determination of apparent density ISO 3923-1-79. Part 2. Scott volumeter method.
108. Keyence Microscopes. Iegūts no: [www.keyence.com/products/microscope/index.jsp](http://www.keyence.com/products/microscope/index.jsp)
109. Dilatometry (DIL). Iegūts no: <https://www.netzsch-thermal-analysis.com/en/products.../dilatometer>
110. Multipurpose X-ray diffraction system. Iegūts: <https://www.rigaku.com/en/products/xrd/ultima>
111. Mixer-Dispenser. Patent DE202007014913U1. Iegūts no: <https://patents.google.com/patent/DE202007014913U1/de>
112. Mironov V., Kolosov V. Lifting of powder materials. Patent of Latvia – LV 12785 B, Int. cl. 7 B65G54/02, H02K44/02, 20.03.2002.

113. Пилиневич Л.П. и др. Пористые порошковые материалы с анизотропной структурой для фильтрации жидкостей и газов. Минск, 2005. 252 с. | ISBN985-6760-59-3/
114. Durkee J. Cleaning with Solvents: Methods and Machinery, 2014. 370 p.
115. Микроскопы биологические "БИОЛАМ 70".  
Iegūts no: <http://www.laboratorium.dp.ua/item/20/manual>
116. Дружинин П.В., Новиков Л.Ф., Лысыков Ю.А. Связывающая способность сорбентов. Iegūts no: [http://on-line-wellness.com/view\\_post.php?id=124](http://on-line-wellness.com/view_post.php?id=124)
117. Beckman C., Inc. (USA). Analizatore SA 3100.
118. Capus J.M. Metal Powders: A Global Survey of Production, Applications and Markets. 2011.
119. Danninger H. Powder manufacturing and processing miniaturisation and nanotechnology in PM powder pressing. Euro PM 2004 Conference Proceedings, 2004.
120. Shishkin A., Mironov V., Goljandin D., Lapkovsky V. Recycling of Al-W-B Composite Material. In: Hussainova, I. (Ed.). Engineering Materials and Tribology. 2013. pp. 143–147. Trans Tech Publications Ltd. (Key Engineering Materials; 527).10.4028. Iegūts no: [www.scientific.net/KEM.527.143](http://www.scientific.net/KEM.527.143)
121. Teibe U. Fizikas medicīniskie aspekti 2.temats. Bioreoloģijas pamati. Rīga, 2006.
122. Mironov V., Prosvirjakov R. Use of iron powder for thermal cutting of concentrate and other materials. Joint nordic conference in Powder Technology, Helsinki, 1997. P. 17-20.
123. Порошкообразный сорбент для сбора нефти, масел и других углеводородов. Patent RU. № 2088534. Iegūts no: <http://www.freepatent.ru/patents/2232633>
124. Магнитоактивные сорбенты на основе природных и синтетических цеолитов. Patent RU No. 2061540. Iegūts no: <http://www.freepatent.ru/patents/2061540>
125. Рубанов Ю.К., Токач Ю.Е., Иванов А.С., Аркатова И.И. Композиционные сорбенты на основе оксидов железа для извлечения углеводородов из водных сред. Фундаментальные исследования. 2014. № 11-8. С. 1692-1697.
126. Sorbent for collecting oil products. Patent of the Republic of Latvia LV 13927 B 20.08.2009, Int. Cl. B01J20/02. Treijs J., Teirumnieks E. Mironovs V., Lapkovskis V., Shishkin A.
127. Немченко А.Г. Обезвреживание и переработка нефтяных шламов.1974.
128. Сжигание нефтяных шламов в печах с кипящим слоем.  
Iegūts no: [www.ru-ecology.info/post/101067000380004](http://www.ru-ecology.info/post/101067000380004)
129. Мукасян А., Рогачев А. Горение для синтеза материалов. Введение в структурную макрокинетику. 2011.
130. Ферромагнитный сорбент из рудного концентрата. Патент SU 1792919. Iegūts no: <http://patents.su/3-1792919-sposob-ochistki-vody-ot-organicheskikh-primesejj.html>
131. Емельянов С.Г. и др. Патент RU 2462303. Порошкообразный магнитный сорбент для сбора нефти, масел и других углеводородов.
132. Мировой рынок меди. Iegūts no: [www.cmmarket.ru/markets/cuworld.htm](http://www.cmmarket.ru/markets/cuworld.htm)
133. Брусницына Л.А., Степановских Е. И. Технология изготовления печатных плат. Екатеринбург, 2015, 200 с.
134. Большая энциклопедия нефти и газа.  
Iegūts no: <http://www.ngpedia.ru/id123268p2.html>
135. Annamalai V., Murr L.E. Influence of deposit morphology on the kinetics of copper cementation on pure iron. Hydrometallurgy. 4, 1997, pp. 57-82.
136. Stefanowicz T., Osinska M., Napieralska-Zagozda, S. Copper recovery by the cementation method. Hydrometallurgy, 47, 1997, pp. 69-90.

137. Polyakov A., Polyakova E. Hydrodynamic cavitation homogenizer. LV 15143, 20.07.2016.
138. Hõganās AB, Cementation processes. 4.4.2.4.2002.
139. Способ извлечения меди из растворов. Патент РФ 2144962. Iegūts no: <http://brevets-patents.ic.gc.ca/opic-cipo/cpd/eng/patent/2144962/summary.html>
140. Миронов В., Земченков В., Лапковский А., Трейс Ю., Савич В. Исследования свойств порошковых ферромагнитных сорбентов для сбора нефтепродуктов с водной поверхности// Экологический вестник. Nr. 1 (23). Минск, Белоруссия. 2013, с. 32–40.
141. Похил П.Ф., Беляев А.Ф., Фролов Ю.В. и др. Горение порошкообразных металлов в активных средах. М.: Наука, 1972.
142. Urpu bonu, naftas produktu noplūdes ierobežojošās barjeras. Iegūts no: <http://deltars.lv/absorbenti/lokalizācijas-bonas>
143. Gudrona dīķu sekas būs jūtamas pat pēc 70 gadiem. Iegūts no: <http://www.lsm.lv/raksts/dzive--stils/veselibā/gudrona-dīķu-sekas-bus-jutamas-pat-pec-70-gadiem.a104309>
144. Nafta un tās īpašības. Iegūts no: <https://teletrade-dj.lv/node/113566>
145. Niftaliyev S.I., Podrezova J.G. Ferromagnetic Sorbent. Voronezh State University of Engineering Technology Voronezh, Russia. Iegūts no: <https://www.rae.ru/forum2012/pdf/0594.pdf>
146. Mironov V., Zemchenkov V., Lapkovskiy V., Treis J., Savich V. Investigation of powder ferromagnetic sorbents properties for petroleum collection from water surface (Исследования свойств порошковых ферромагнитных сорбентов для сбора нефтепродуктов с водной поверхности). Ekologicheskiy vestnik (Экологический вестник). Baltkrievija, Minsk. 2013, 1(23), pp. 32-40.
147. Kūdra. Iegūts no: <http://mapx.map.vgd.gov.lv/g3inflv/noveroumi/nv08.htm>
148. Tūmanok A., Kulu P. Treatment of different materials by disintegrator systems. In Proc. Estonian Acad. Sci. Eng., 5, 3 (1999), 222-242.
149. Белов В.В. Капиллярное структурообразование сырьевых композиций на основе минеральных вяжущих веществ. ALIIFORM, № 6, 2010, С. 63-75.
150. Prasības tērauda velmēšanas iekārtām un iekārtu tehniskās uzraudzības kārtība. Iegūts no: <https://likumi.lv/ta/id/53425-prasibas-terauda-velmesanas-iekartam-un-iekartu-tehniskas-uzraudzibas-kartiba>
151. Plazmas loka un citi termiskās griešanas veidi. Iegūts no: <http://svarka.n-stars.org/t40-plazmas-loka-un-citi-termiskas-griesanas-veidi>.
152. Каблов В.Ф и др. Экономическая эффективность применения в опытном производстве целлюлозосодержащих материалов в качестве сорбентов для поглощения нефтепродуктов // Научно-методический электронный НаВННО методический журнал «Концепт». 2017. № 5 (май). 0,3 п. л. Iegūts no: <http://e-kon-электронный журнал sertru/2017/170100.htm>
153. Обзор избранных предприятий по переработке и утилизации. Iegūts no: [https://www.barentsinfo.fi/.../Report\\_May\\_2013\\_Selection\\_of\\_facilities\\_for\\_treatment](https://www.barentsinfo.fi/.../Report_May_2013_Selection_of_facilities_for_treatment)
154. Būvējam labāku nākotni Iegūts no: [www.cemex.lv/corvus.lv/2013-07-25-13-51-45](http://www.cemex.lv/corvus.lv/2013-07-25-13-51-45).
155. Измельчение торфа и торфо-сапропеля. Iegūts no: [www.saprex.agroserver.ru/articles/1724](http://www.saprex.agroserver.ru/articles/1724)
156. Сила притяжения постоянного магнита. Супермагниты. Iegūts no: [www.supermagnit.od.ua/magnetizm.php](http://www.supermagnit.od.ua/magnetizm.php).
157. Регенерация сорбентов. Iegūts no: [engineeringssystem.ru/r/regeneracia-sorbentov.php](http://engineeringssystem.ru/r/regeneracia-sorbentov.php)
158. Способ очистки воды от органических примесей. Patent SU 1792919. Iegūts no: <http://patents.su/3-1792919-sposob-ochistki-vody-ot-organicheskikh-primesejj.html>

159. Plazmas loka un citi termiskās griešanas veidi.  
<http://svarka.n-stars.org/t40-plazmas-loka-un-citi-termiskas-griesanas-veidi>.
160. Каблов В. Ф и др. Экономическая эффективность применения в опытном производстве целлюлозосодержащих материалов в качестве сорбентов для поглощения нефтеразливов // Научно-методический электронный НаВННО методический журнал «Концепт». - 2017. - № 5 (май).- 0,3 п. л. -  
URL: [http://e-kon-электронный журнал sertru/2017/170100.htm](http://e-kon-электронный_журнал_sertru/2017/170100.htm).
161. Обзор избранных предприятий по переработке и утилизации  
[https://www.barentsinfo.fi/.../Report\\_May\\_2013\\_Selection\\_of\\_facilities\\_for\\_treatment...](https://www.barentsinfo.fi/.../Report_May_2013_Selection_of_facilities_for_treatment...)
162. Būvējam labāku nākotni | CEMEX [www.cemex.lv/corvus.lv/2013-07-25-13-51-45](http://www.cemex.lv/corvus.lv/2013-07-25-13-51-45).
163. Измельчение торфа и торфо-сапропеля. [saprex.agroserver.ru/articles/1724/](http://saprex.agroserver.ru/articles/1724/)
164. Сила притяжения постоянного магнита - Супермагниты.  
[www.supermagnit.od.ua/magnetizm.php](http://www.supermagnit.od.ua/magnetizm.php).
165. [engineeringssystem.ru/r/regeneracia-sorbentov.php](http://engineeringssystem.ru/r/regeneracia-sorbentov.php)
166. patent SU 1792919

## APPENDICES





**Juris Treijs** was born in Preiļi in 1978. He received a Bachelor degree of Engineering Science in Construction Science from Riga Technical University. In 2004, he obtained a professional Engineering Master's degree in Transport Constructions from RTU, and since 2003, he has been working in the road construction area.

Since joining RTU in 2015, he has been with the Powder Materials Research Laboratory, the results of his work have been approved by two Latvian patents.